

DTIC FILE COPY -

4

APPROVED FOR PUBLIC RELEASE
DISTRIBUTION UNLIMITED

REPORT NO. 88-R-07
AFPEA PROJECT NO. 87-P-111
88-P-116

AD-A205 198

Susan M. Hughey

Mechanical Engineer

AUTOVON 787-3362

Commercial (513) 257-3362

DTIC
ELECTE
FEB 17 1989
S & H D

EVALUATION OF ENGINEERING CHANGE PROPOSALS 10 AND 31
AND PERFORMANCE ORIENTED PACKAGING TESTING OF
CNU-399E/425E FIBERGLASS MAVERICK MISSILE CONTAINER

HQ AFLC/DSTZ
AIR FORCE PACKAGING EVALUATION ACTIVITY
Wright-Patterson AFB OH 45433-5999

24 JANUARY 1989

DISTRIBUTION STATEMENT A

Approved for public release;
Distribution Unlimited

09 2 16 181

NOTICE

When government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related government procurement operation, the United States Government thereby incurs no responsibility whatsoever, and the fact that the government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation or conveying any rights or permission to manufacture use or sell any patented invention that may in any way be related thereto. This report is not to be used in whole or part for advertising or sales purposes.

ABSTRACT

Aeronautical Systems Division, ASD/SDML, requested assistance from the Air Force Packaging Evaluation Activity to conduct testing on the CNU-399E/425E fiberglass Maverick missile container for engineering change proposals and performance oriented packaging.

The CNU-399E/425E container was designed and fabricated by Plastics Research Corporation, 13538 Excelsior Dr., Santa Fe Springs CA 90670. The containers are environmentally sealed with a humidity indicator, desiccant port, and a pressure relief valve. The containers are designed to protect one AGM-65A/B/C/D/E/F all-up-round Maverick missile during world-wide shipment, storage, and handling. The containers will also be used for one missile without the guidance unit and for one missile without the guidance unit and the hydraulic actuation system. The CNU-425/E is the Air Force version of the container. The CNU-399/E is the Navy version and differs from the CNU-425/E only in some external Navy-specific handling features. — (REF) 7

The test plan used for these containers was derived from ASD/SDML Specification Number CON 319 dated 30 May 86, Federal Test Method Standard No. 101, U.N. Standard (Ref. ICAD 4.3).

Results of the tests conducted on the containers were acceptable. The container's cradle system did not crack during the rough handling tests and the containers did successfully pass the POP tests, as prescribed by the UN test criteria.

PREPARED BY:

Susan Hughey
Susan Hughey
Mechanical Engineer
AFPEA

PUBLICATION DATE:

26 JAN 1989

REVIEWED BY:

Ted Hinds
Ted Hinds
Ch, Design Branch
AFPEA

APPROVED BY:

Charlie P. Edmonson
Charlie P. Edmonson
Chief, AF Packaging
Evaluation Activity

TABLE OF CONTENTS

	<u>Page</u>
ABSTRACT.....	i
TABLE OF CONTENTS.....	ii
INTRODUCTION	
BACKGROUND.....	1
PURPOSE.....	1
TEST SPECIMEN.....	1
TEST OUTLINE AND TEST EQUIPMENT.....	1
TEST PROCEDURES AND RESULTS.....	2
TEST NO. 1, INSPECTION.....	2
TEST NO. 2, LEAK TEST.....	2
TEST NO. 3A, EDGEWISE-DROP (ROTATIONAL) (+140°F) TEST..	2
TEST NO. 3B, CORNERWISE-DROP (ROTATIONAL) (+140°F) TEST	3
TEST NO. 3C, PENDULUM-IMPACT (+140°F) TEST.....	3
TEST NO. 4A, EDGEWISE-DROP (ROTATIONAL) (-40°F) TEST...	3
TEST NO. 4B, CORNERWISE-DROP (ROTATIONAL) (-40°F) TEST.	3
TEST NO. 4C, PENDULUM-IMPACT (-40°F) TEST.....	3
TEST NO. 5, LEAK TEST.....	3
TEST NO. 6A, SQUARING BLOCK SUPPORT TEST, EDGE ROLL....	4
TEST NO. 6B, SQUARING BLOCK SUPPORT TEST, SIDE BY SIDE.	4
TEST NO. 6C, SQUARING BLOCK SUPPORT TEST, SIDE IMPACT..	4
TEST NO. 7, LEAK TEST.....	4
TEST NO. 8, INSPECTION.....	4
TEST NO. 9, UN DROP TEST.....	4
TEST NO. 10, UN STACKING TEST.....	5



By _____	
Distribution/ _____	
Availability Codes	
Dist	Avail and/or Special
A-1	

TABLE OF CONTENTS (CONTINUED)

	<u>Page</u>
CONCLUSION.....	5
TABLE I, CONTAINER TEST PLAN.....	6
FIGURE 1, CONTAINER CONFIGURATION.....	11
FIGURE 2, UN DROP TEST, SIDE 3.....	12
FIGURE 3, UN DROP TEST, TOP.....	12
FIGURE 4, DAMAGE TO SIDE 3.....	13
FIGURE 5, SIDE 2 FORWARD STRAP.....	13
FIGURE 6, SIDE 2 AFT STRAP.....	14
FIGURE 7, DISENGAGED LATCH, SIDE 4 FORWARD CLAMP.....	14
FIGURE 8, DISENGAGED LATCH, SIDE 2 AFT CLAMP.....	15
FIGURE 9, DISENGAGED LATCH, SIDE 4 AFT CLAMP.....	15
FIGURE 10, DAMAGED FORWARD CLAMP.....	16
FIGURE 11, BENT FIN, SIDE 2 OF MISSILE.....	16
FIGURE 12, DELAMINATION ON SIDE 3 OF COVER.....	17
FIGURE 13, CRADLE CUSHION, TORN AND UNGLUED.....	17
REPORT DOCUMENTATION PAGE.....	18
DISTRIBUTION LIST.....	20

INTRODUCTION

BACKGROUND: Aeronautical Systems Division, ASD/SDML, requested assistance from the Air Force Packaging Evaluation Activity to conduct testing on the CNU-399E/425E fiberglass Maverick missile container for engineering change proposals (ECP) and performance oriented packaging (POP) testing. The CNU-399E/425E container was designed and fabricated by Plastics Research Corporation (PRC), 13538 Excelsior Dr., Santa Fe Springs CA 90670.

PURPOSE: The purpose of this project was to determine whether testing the CNU-399E/425E container would damage the squaring blocks (ECP 7: adding squaring blocks to the container configuration) or the cradle system (ECP 31: changing the cradle clamp fabrication process from open mold to compression mold) and whether the container would spill its contents (POP testing). The container is designed to protect one AGM-65A/B/C/D/E/F all-up-round Maverick missile during world-wide shipment, storage, and handling. The container will also be used for one missile without the guidance unit and for one missile without the guidance unit and the hydraulic actuation system. The CNU-425/E is the Air Force version of the container. The CNU-399/E is the Navy version and differs from the CNU-425/E only in some external Navy-specific handling features. The United Nations (UN) hazard code for the missile is class 1.1F. The packing code is Group II, with the packing method of E146.

TEST SPECIMEN

Four CNU-425/E containers (serial numbers 83-25120, 83-25121, 83-25385 and 25386) were sent from PRC. The corners of the containers were numbered from the aft end (see figure 1).

DESIGN: The containers are environmentally sealed with a humidity indicator, desiccant port, and a pressure relief valve. The container is designed to limit the transmission of shocks to the missile at 40G or less when subjected to the conditions in ASD/SDML Specification CON 319. Twenty t-bolts attach the container cover to the container base. The missile is attached to the cradle system by forward and aft clamps.

CONSTRUCTION: The container consists of a fiberglass reinforced plastic cover, base, cradle, forward clamp and aft clamp, which have been gel coated. Rubber pads between the missile and the cradle prevent scratching or scarring of the missile body. Two pound density polyethylene foam provides cushioning between the cradle and the container base. A neoprene (or equivalent) gasket provides a seal between the container base and the container cover.

TEST OUTLINE AND TEST EQUIPMENT

TEST PLAN: Tests were conducted in accordance with table I. Test methods and procedures used were as outlined in Federal Test Method Standard 101 (FTMS No. 101), Military Standard 648 (MIL-STD-648), U.N. Standard (Ref. ICAD 4.3) and ASD/SDML Specification CON 319 dated 30 May 86. Any modifications to the standard procedures are noted in the test plan or the results.

TEST CONTAINERS: The tests in this report were performed on CNU-425/E, serial number 83-25121 except for the UN stacking test (test no. 10) where the CNU-425/E, serial number 83-25120 was used. Only one container was used for UN drop tests (test no. 9) since the tests were severe and it would be too costly to provide a new container for each drop.

TEST LOADS: All tests were conducted using the standard heavy test load weighing 670 pounds. A container base loaded with 3150 pounds (three times the gross weight of a container with a heavy standard load) was also used for test number 10 to simulate stacked containers.

TEST SITES: Testing was conducted at AFPEA, HQ AFLC/DSTZ, Building 70, Area C, Wright-Patterson AFB OH. The equipment required for testing was a temperature chamber and a forklift truck.

TEST PROCEDURES AND RESULTS

INSPECTION

Test No. 1: The containers, as received, were visually inspected. The exterior and interior surfaces, hardware, cushioning, markings, and container seal were inspected.

Results: All container features were found to be acceptable.

LEAK TEST

Test No. 2: The pneumatic pressure test was conducted in accordance with FTMS No. 101, Method 5009.2. The test was performed at 1.00 psig. The failure criteria for the test was 0.013 psig loss during a 15 minute period.

Results: At the end of the 15 minute test period, container 83-25121 had a pressure test leak rate of 0.012 psig. No leaks were evident on the container. The results of this test are acceptable.

ROUGH HANDLING TESTS (+140°F)

Test No. 3A: The high temperature edgewise-drop (rotational) test was conducted in accordance with FTMS No. 101, Method 5008.1. The height of the drop was 20 inches.

Results: Visual inspection revealed no apparent damage to the exterior of container 83-25121.

Test No. 3B: The high temperature cornerwise-drop (rotational) test was conducted in accordance with FTMS No. 101, Method 5005.1. The height of the drop was 20 inches.

Results: Visual inspection revealed no apparent damage to the exterior of container 83-25121.

Test No. 3C: The high temperature pendulum-impact test was conducted in accordance with FTMS No. 101, Method 5012. The impact velocity was 7 ft/sec from a drop height of 9.0 inches.

Results: Visual inspection revealed no apparent damage to the exterior of container 83-25121.

The container 83-25121 was opened and the container straps had loosened. Also, two small gouges were evident on the forward clamp. It should be noted that the strap design had changed to a folded, no twist configuration from a closed loop, twisted configuration.

ROUGH HANDLING TESTS (-40°F)

Test No. 4A: The low temperature edgewise-drop (rotational) test was conducted in accordance with FTMS No. 101, Method 5008.1. The height of the drop was 20 inches.

Results: Visual inspection revealed no apparent damage to the exterior of container 83-25121.

Test No. 4B: The low temperature cornerwise-drop (rotational) test was conducted in accordance with FTMS No. 101, Method 5005.1. The height of the drop was 20 inches.

Results: Visual inspection revealed no apparent damage to the exterior of container 83-25121.

Test No. 4C: The low temperature pendulum-impact test was conducted in accordance with FTMS No. 101, Method 5012. The impact velocity was 7 ft/sec from a drop height of 9.0 inches.

Results: Visual inspection revealed no apparent damage to the exterior of container 83-25121.

The container 83-25121 was opened and the container straps had loosened further. Also, the rubber padding on the forward clamp was deformed.

LEAK TEST

Test No. 5: The pneumatic pressure test was conducted in accordance with FTMS No. 101, Method 5009.2. The test was performed at 1.00 psig. The failure criteria for the test was 0.013 psig loss during a 15 minute period.

Results: At the end of the 15 minute test period, container 83-25121 had a pressure test leak rate of 0.000 psig. It should be noted that the room temperature rose from 24.9°C to 25.1°C during the leak test and leaks were evident around the forkwell bolt below t-bolt 18 and at t-bolt 14. The results of this test are acceptable.

SQUARING BLOCK SUPPORT TEST

Test No. 6A: The edge roll was conducted to determine whether impacting the squaring block would influence the seal of container 83-25121.

Test No. 6B: The side by side impact was conducted to determine whether impacting the squaring block would influence the seal of container 83-25121.

Test No. 6C: The side impact was conducted to determine whether impacting the squaring block would influence the seal of container 83-25121.

LEAK TEST

Test No. 7: The pneumatic pressure test was conducted in accordance with FTMS No. 101, Method 5009.2. The test was performed at 1.00 psig. The failure criteria for the test was 0.013 psig loss during a 15 minute period.

Results: At the end of the 15 minute test period, container 83-25121 had a pressure test leak rate of 0.000 psig. It should be noted that the room temperature rose from 25.1°C to 25.3°C during the leak test and leaks were evident around the forkwell bolt below t-bolt 18 and at t-bolt 14. The results of this test are acceptable.

INSPECTION

Test No. 8: Container 83-25121 was visually inspected. The exterior and interior surfaces, hardware, cushioning, markings, and container seal were inspected.

Results: Abrasion damage was evident on the squaring blocks on side 2 of container 83-25121. The results of this test are acceptable.

UN DROP TEST

Test No. 9: Container 83-25121 was conditioned at 32°F for 24 hours then dropped flat on the bottom, side 4 (long side), side 3 (short side, see figure 2), the top (see figure 3) and top corner 2-3. The container shall not spill its contents.

Results: Visual inspection revealed that side 3 and the top corner 2-3 had deformed (see figure 4). The container was opened and the following damage was found: the forward and aft straps on side 2 broke (see figure 5 and 6); the latches disengaged on side 4 of the forward clamp (see figure 7), on side 2 of the aft clamp (see figure 8) and on side 4 of the aft clamp (see figure 9); the missile traveled inside the container damaging the top portion of the forward clamp (see figure 10), bending the fin on side 2 of the missile (see figure 11), delaminating side 3 on the cover (see figure 12) and crushing the desiccant basket; and the cradle cushion was torn and unglued from the container base (see figure 13). However, the container did not spill its contents. Results of this test are acceptable.

UN STACKING TEST

Test No. 10: At ambient temperature, a superimposed load of 3150 pounds was placed on container 83-25120 for 24 hours. The container shall not permanently deform.

Results: Container 83-25120 was dimensionally checked and no permanent deformation occurred during the stacking test. The results of this test are acceptable.

CONCLUSION

1. The container successfully passed the squaring block tests and did not affect the container seal.
2. The container successfully passed the high and low temperature rough handling test without cracking the clamps on the cradle system.
3. The container successfully passed the POP tests, as prescribed by the UN test criteria.

TABLE I.

AIR FORCE PACKAGING EVALUATION ACTIVITY (Container Test Plan)						AFPEA PROJECT NUMBER	
						88-P-116, 87-P-111	
CONTAINER SIZE (L x W x D) (INCHES)		WEIGHT (LBS)		CUBE (CU. FT.)	QUANTITY	DATE	
INTERIOR:	EXTERIOR:	GROSS:	ITEM:				
	110x32x30	1050	670	61		11 Jan 89	
ITEM NAME				MANUFACTURER			
AGM-65 Maverick Missile				Plastics Research Corporation			
CONTAINER NAME						CONTAINER COST	
CNU-399/E and CNU-425/E (UN Tests, ECPs 10 & 31)						\$1200	
PACK DESCRIPTION							
Fiberglass Container							
CONDITIONING							
As noted below.							
TEST NO.	REF STD/SPEC AND TEST METHOD OR PROCEDURE NO'S	TEST TITLE AND PARAMETERS		CONTAINER ORIENTATION	INSTRUMENTATION		
1.	<u>INSPECTION</u>	Visually inspect container before testing.					
2.	<u>LEAK TEST</u> FED-STD-101 Method 5009.2 *(4.2.2.1.13)	Pneumatic pressure at 1.00 PSI. Test duration to be a minimum of 15 minutes. Leakage rate shall not exceed 0.05 PSI/HR after temperature stabilization.		Test at ambient condition from compressed air supply/vacuum pump.	Water manometer		
3.	<u>ROUGH HANDLING TESTS (HIGH TEMPERATURE +140°F)</u>						
a.	FED-STD-101 Method 5008.1 (4.2.2.1.7)	Edgewise-drop (rotational) test. Condition at +140°F for not less than 24 hours. Drop height 20 inches.		Test performed in chamber. One drop on 2 adjacent bottom edges, total of 2 drops.** Test w/ heaviest AUR.			
b.	FED-STD-101 Method 5005.1 (4.2.2.1.7)	Cornerwise-drop (rotational) test. Condition at +140°F for not less than 24 hours. Drop height 20 inches.		Test performed in chamber. One drop on diagonal bottom corners, total of two drops.***			
COMMENTS: * Figures in parenthesis refer to paragraph in Spec. No. CON 319. ** Remaining edge drops to be performed in Test No. 4a. *** Remaining corner drops to be performed in Test No. 4b.							
PREPARED BY: <i>Susan Hughey</i>				APPROVED BY:			
Susan Hughey, Mechanical Engineer				TED HINDS, Chief, Design Br., AFPEA			

AIR FORCE PACKAGING EVALUATION ACTIVITY (Container Test Plan)						AFPEA PROJECT NUMBER	
CONTAINER SIZE (L x W x D) (INCHES)		WEIGHT (LBS)		CUBE (CU. FT.)	QUANTITY	DATE	
INTERIOR: EXTERIOR:		GROSS:	ITEM:				
110x32x30		1050	670	61		11 Jan 89	
ITEM NAME				MANUFACTURER			
AGM-65 Maverick Missile				Plastics Research Corporation			
CONTAINER NAME					CONTAINER COST		
CNU-399/E and CNU-425/E (UN Tests, ECPS 10 & 31)					\$1200		
PACK DESCRIPTION							
Fiberglass Container							
CONDITIONING							
As noted below.							
TEST NO.	REF STD/SPEC AND TEST METHOD OR PROCEDURE NO'S	TEST TITLE AND PARAMETERS		CONTAINER ORIENTATION	INSTRUMENTATION		
c.	FED-STD-101 Method 5012 (4.2.2.1.7)	Pendulum-impact test. Condition at +165°F. Temperature of shock mitigation system at time of test shall be +140(±5°F). Impact velocity 7 ft/sec*, drop height 9 inches.		Test with heaviest AUR. One impact on each side and each end, total of four impacts. Test with heaviest AUR.			
4.	<u>ROUGH HANDLING TESTS (LOW TEMPERATURE -40°F)</u>						
a.	FED-STD-101 Method 5008.1 (4.2.2.1.8)	Edgewise-drop (rotational) test. Condition at -40°F for not less than 24 hours. Drop height 20 inches.		Test performed in chamber. One drop on two adjacent bottom edges, total of two drops.** Test with heaviest AUR.			
b.	FED-STD-101 Method 5005.1 (4.2.2.1.7)	Cornerwise-drop (rotational) test. Condition at -40°F for not less than 24 hours. Drop height 20 inches.		Test performed in chamber. One drop on diagonal bottom corners, total of two drops.*** Test with heaviest AUR.			
COMMENTS: * Impact velocity revised per ASD/TAML letter dated 24 Aug 87. ** These edges are opposite those impacted in Test No. 3a. *** These corners are opposite those impacted in Test No. 3b.							
PREPARED BY:				APPROVED BY:			
Susan Hughey, Mechanical Engineer				TED HINDS, Chief, Design Br., AFPEA			

AIR FORCE PACKAGING EVALUATION ACTIVITY (Container Test Plan)					AFPEA PROJECT NUMBER	
CONTAINER SIZE (L x W x D)(INCHES)			WEIGHT (LBS)		CUBE (CU. FT.)	
INTERIOR:		EXTERIOR:	GROSS:	ITEM:	QUANTITY	DATE
110x32x30			1050	670	61	11 Jan 89
ITEM NAME				MANUFACTURER		
AGM-65 Maverick Missile				Plastics Research Corporation		
CONTAINER NAME					CONTAINER COST	
CNU-399/E and CNU-425/E (UN Tests, ECPs 10 & 31)					\$1200	
PACK DESCRIPTION						
Fiberglass Container						
CONDITIONING						
As noted below.						
TEST NO.	REF STD/SPEC AND TEST METHOD OR PROCEDURE NO'S	TEST TITLE AND PARAMETERS	CONTAINER ORIENTATION	INSTRUMENTATION		
c.	FED-STD-101 Method 5012 (4.2.2.1.7)	Pendulum-impact test. Condition at -65°F. Temperature of shock mitigation system at time of test shall be -40 (±5°F). Impact velocity 7 ft/sec*, drop height 9 inches.	One impact on each side and each end, total of four impacts. Test with heaviest AUR.			
5.	<u>LEAK TEST</u> FED-STD-101 Method 5009.2 (4.2.2.1.13)	Pneumatic pressure with 1.00 PSI. Test duration not less than 15 minutes. Leakage rate shall not exceed 0.05 PSI/HR after temperature stabilization.	Ambient	Water manometer		
6.	<u>SQUARING BLOCK SUPPORT TEST</u>					
a.	Edge Roll:	Lift loaded container with squaring blocks up on edge and allow to roll on its side.	Test with heaviest AUR.	Forklift truck		
COMMENTS: * Impact velocity revised per ASD/TAML letter dated 24 Aug 87.						
PREPARED BY: Susan Hughey, Mechanical Engineer				APPROVED BY: TED HINDS, Chief, Design Br., AFPEA		

AIR FORCE PACKAGING EVALUATION ACTIVITY**(Container Test Plan)****AFPEA PROJECT NUMBER**

88-P-116, 87-P-111

CONTAINER SIZE (L x W x D) (INCHES)**INTERIOR:****EXTERIOR:**

110x32x30

WEIGHT (LBS)**GROSS:**

1050

ITEM:

670

CUBE (CU. FT.)

61

QUANTITY**DATE**

11 Jan 89

ITEM NAME

AGM-65 Maverick Missile

MANUFACTURER

Plastics Research Corporation

CONTAINER NAME

CNU-399/E and CNU-425/E (UN Tests, ECPs 10 & 31)

CONTAINER COST

\$1200

PACK DESCRIPTION

Fiberglass Container

CONDITIONING

As noted below.

TEST NO.	REF STD/SPEC AND TEST METHOD OR PROCEDURE NO'S	TEST TITLE AND PARAMETERS	CONTAINER ORIENTATION	INSTRUMENTATION
b.	Side by Side:	Place container 1 (loaded) side by side with container 2 (squaring blocks attached). With a forklift, lift container 1 to approximately 30 inches. Move container 1 so its flange area is directly above the squaring blocks of container 2. Allow container 1 to drop, impacting the squaring blocks of container 2.	Test with heaviest AUR.	Forklift truck
c.	Side Impact:	Lift a loaded container with a forklift truck to 18 inches. Side impact a loaded stationary container that has squaring blocks with the loaded container. The forklift truck carrying the loaded container shall impact the loaded stationary container at a speed of 5 ft/sec.	Test with heaviest AUR.	Forklift truck

COMMENTS:**PREPARED BY:**

Susan Hughey, Mechanical Engineer

APPROVED BY:

TED HINDS, Chief, Design Br., AFPEA

AIR FORCE PACKAGING EVALUATION ACTIVITY						AFPEA PROJECT NUMBER	
(Container Test Plan)						88-P-116, 87-P-111	
CONTAINER SIZE (L x W x D) (INCHES)		WEIGHT (LBS)		CUBE (CU. FT.)	QUANTITY	DATE	
INTERIOR:	EXTERIOR:	GROSS:	ITEM:	61		11 Jan 89	
		110x32x30	1050	670			
ITEM NAME				MANUFACTURER			
AGM-65 Maverick Missile				Plastics Research Corporation			
CONTAINER NAME					CONTAINER COST		
CNU-399/E and CNU-425/E (UN Tests, ECPS 10 & 31)					\$1200		
PACK DESCRIPTION							
Fiberglass Container							
CONDITIONING							
As noted below.							
TEST NO.	REF STD/SPEC AND TEST METHOD OR PROCEDURE NO'S	TEST TITLE AND PARAMETERS	CONTAINER ORIENTATION	INSTRUMENTATION			
7.	<u>LEAK TEST</u> FED-STD-101 Method 5009.2 (4.2.2.1.13)	Pneumatic pressure with 1.00 PSI. Test duration not less than 15 minutes. Leakage rate shall not exceed 0.05 PSI/HR after temperature stabilization.	Ambient	Water manometer			
8.	<u>INSPECTION</u>	Visually inspect. Note any damage to squaring block and squaring block attachment points.					
9.	<u>UN DROP TEST</u> *(9.7.3)	Condition at +32°F for not less than 24 hours. Drop height 1.2m (3.94 ft) as required for Packaging Group II. The container shall not spill its contents. A different container may be used for each drop.	One each flat drop on the bottom, top, long side, short side and a corner. Total of 5 drops. Test with the heaviest AUR.				
10.	<u>UN STACKING TEST</u> *(9.7.6)	Simulate stacking to a minimum height of 3m (9.84 ft) for 24 hours. There shall be no permanent deformation.**					
COMMENTS: * Refer to UN "Orange Book" requirements. ** The superimposed load test in MIL-STD-648 exceeds the UN stacking test.							
PREPARED BY: Susan Hughey, Mechanical Engineer				APPROVED BY: TED HINDS, Chief, Design Br., AFPEA			

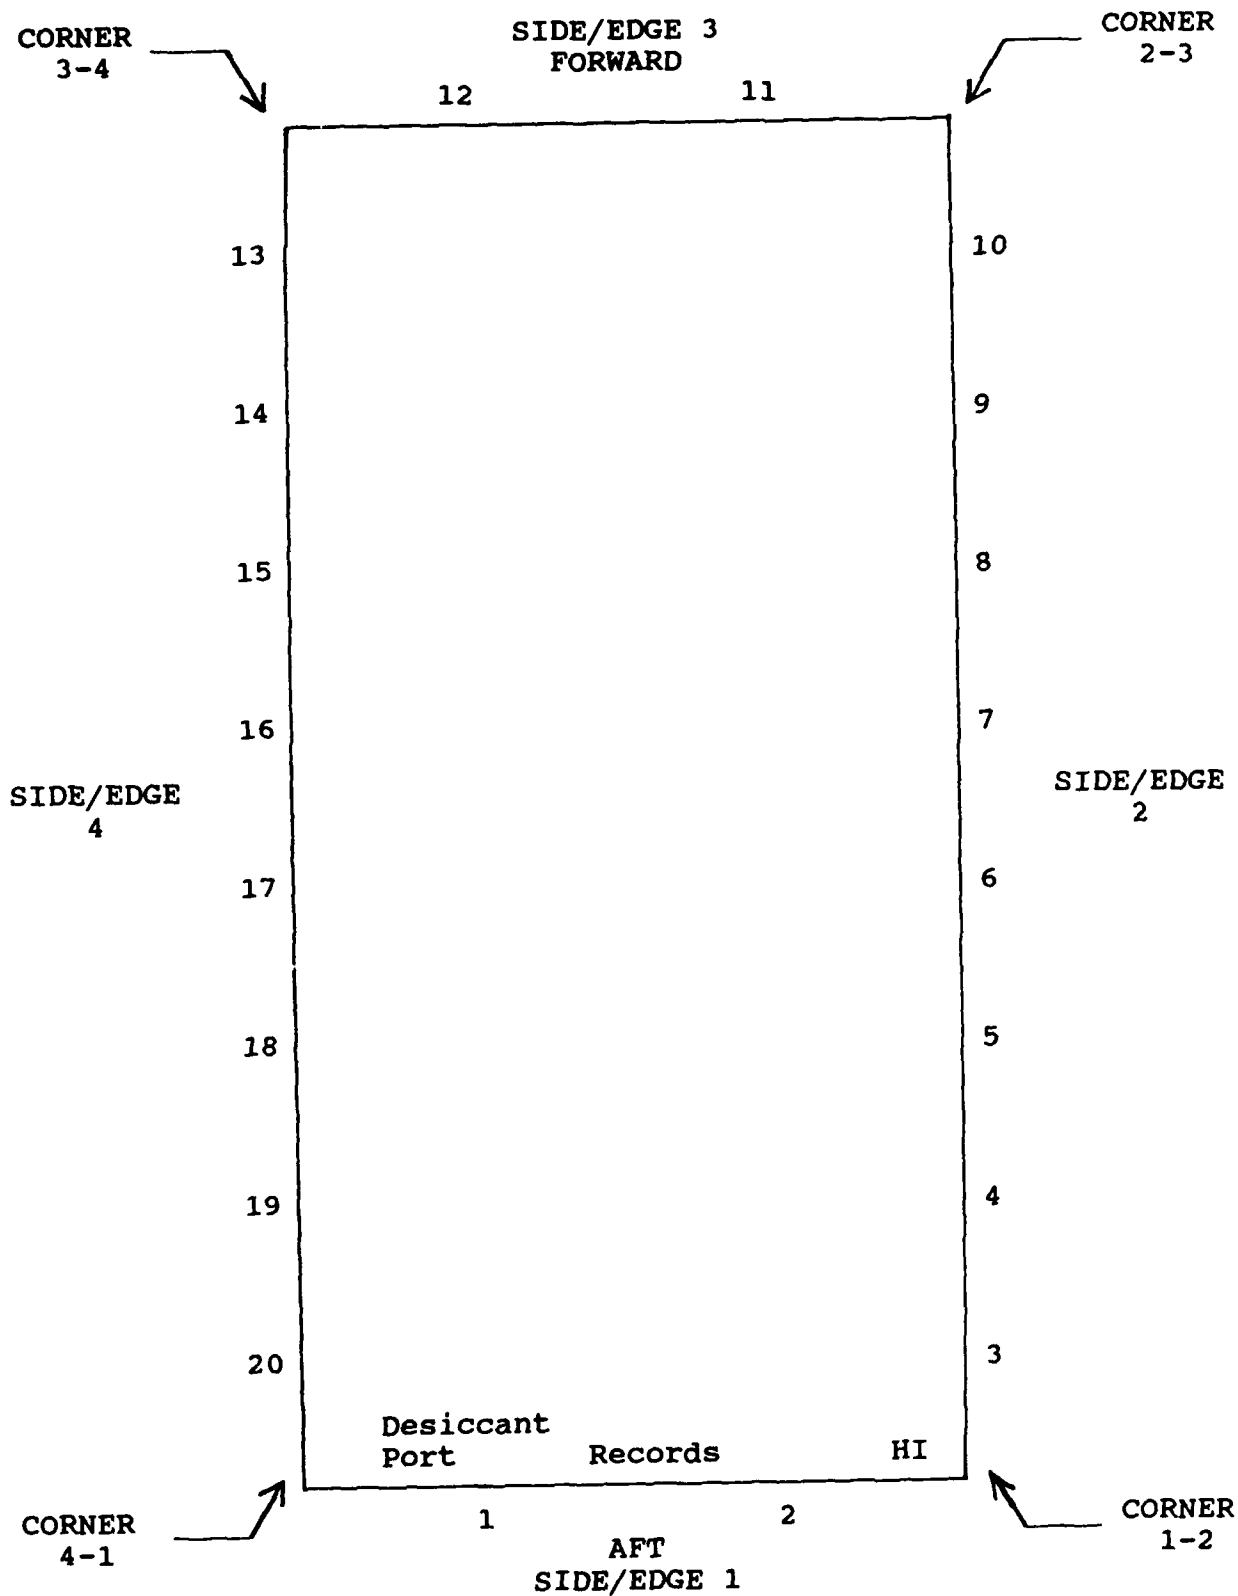


FIGURE 1. CONTAINER CONFIGURATION

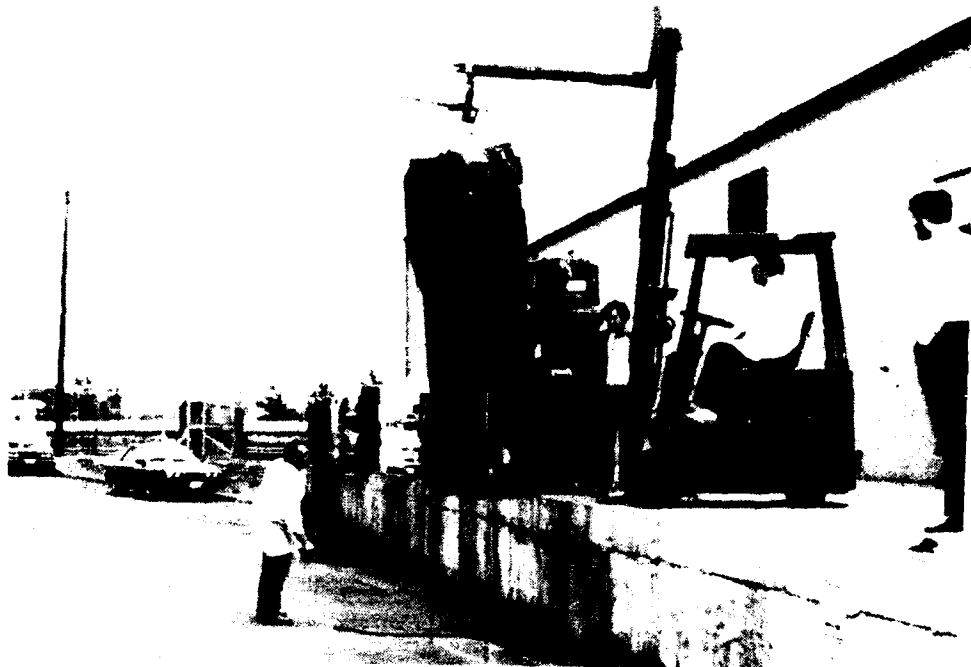


FIGURE 2. UN DROP TEST, SIDE 3.



FIGURE 3. UN DROP TEST, TOP.

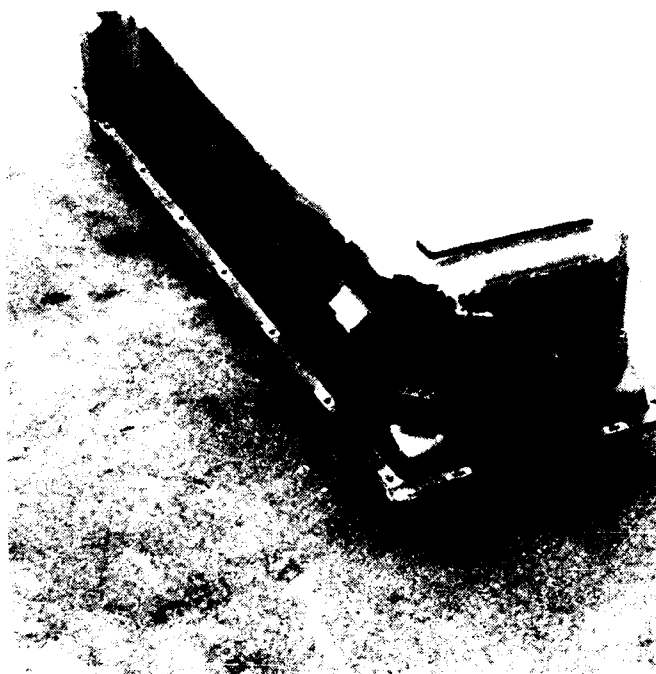


FIGURE 4. DAMAGE TO SIDE 3.

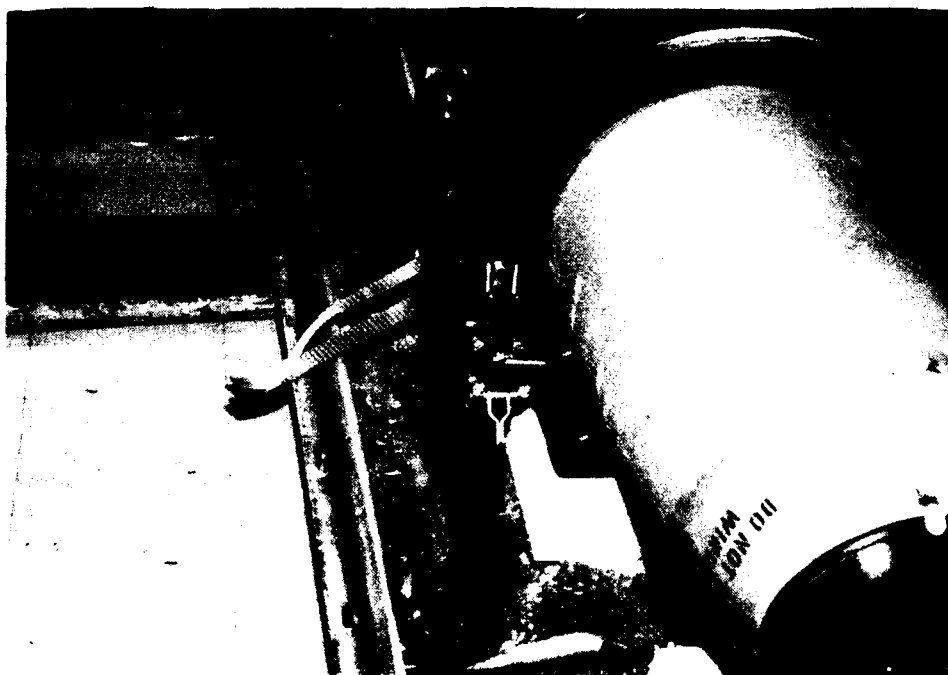


FIGURE 5. SIDE 2 FORWARD STRAP.



FIGURE 6. SIDE 2 AFT STRAP.



FIGURE 7. DISENGAGED LATCH, SIDE 4 FORWARD CLAMP.

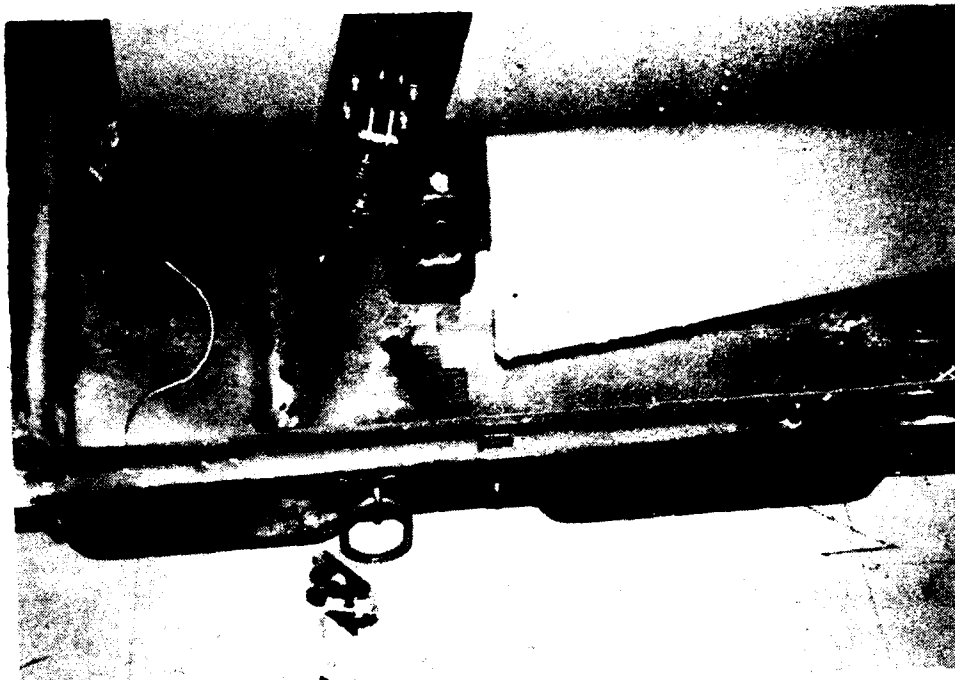


FIGURE 8. DISENGAGED LATCH, SIDE 2 AFT CLAMP.

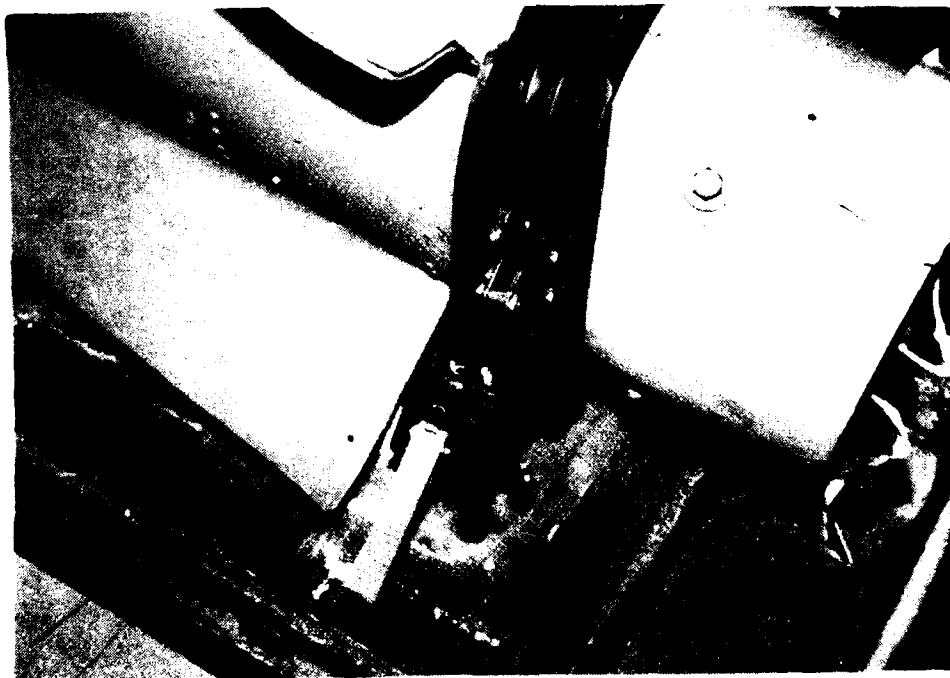


FIGURE 9. DISENGAGED LATCH, SIDE 4 AFT CLAMP.

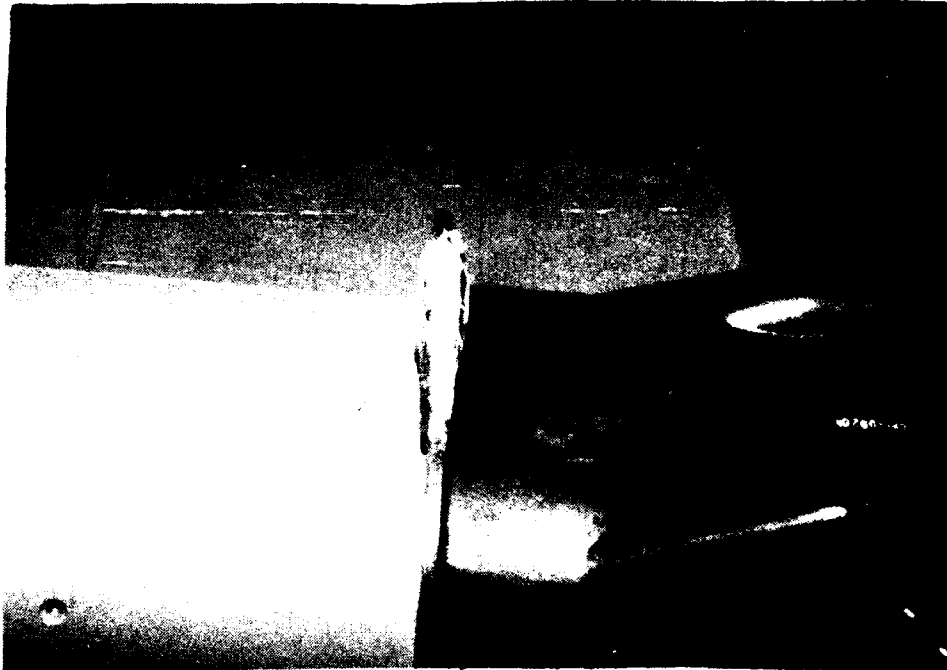


FIGURE 10. DAMAGED FORWARD CLAMP.

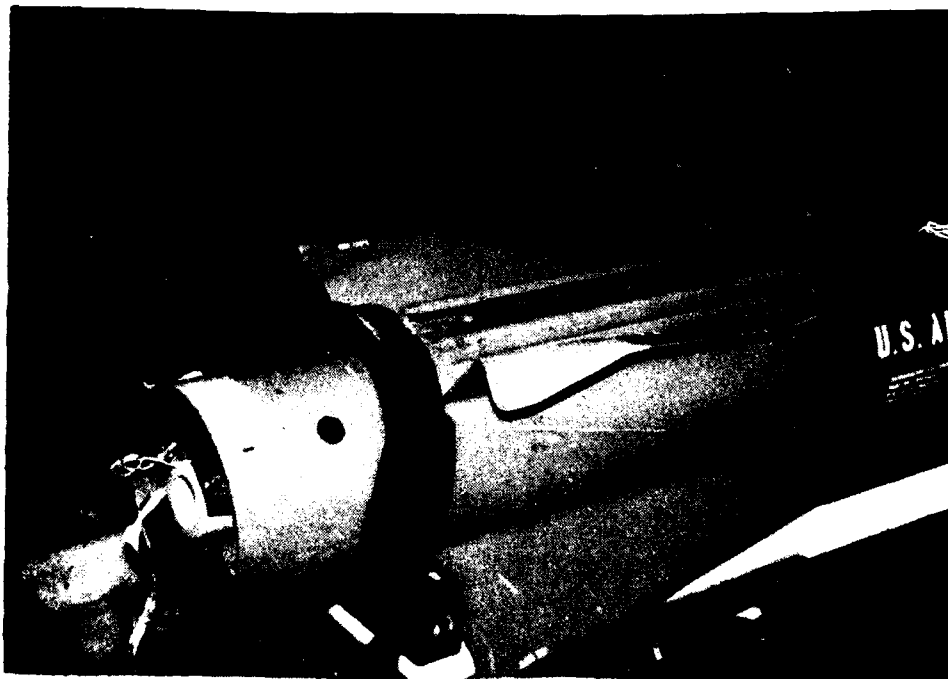


FIGURE 11. BENT FIN, SIDE 2 OF MISSILE.

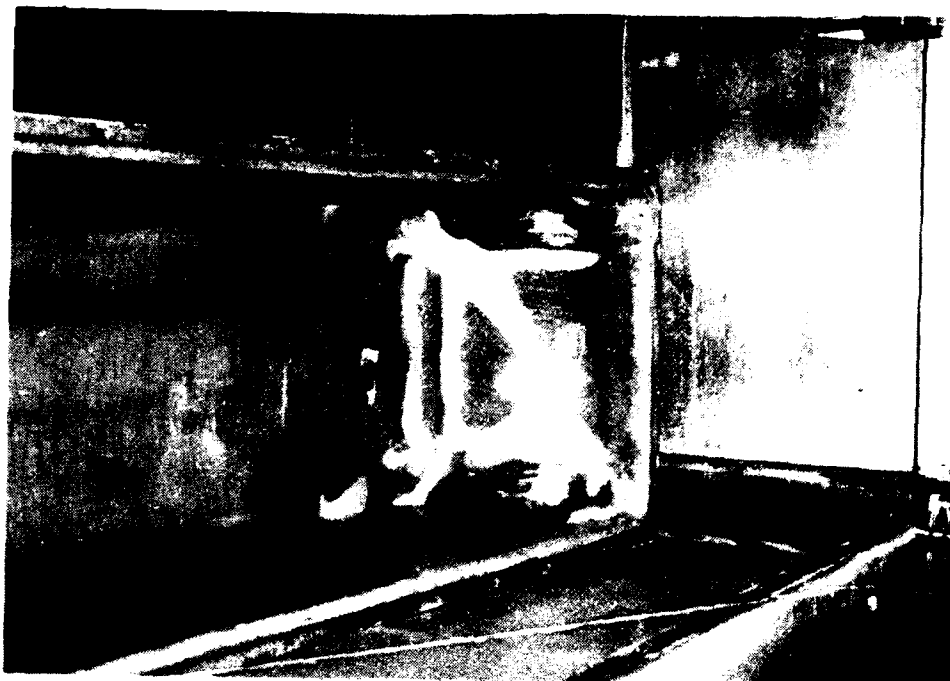


FIGURE 12. DELAMINATION ON SIDE 3 OF COVER.

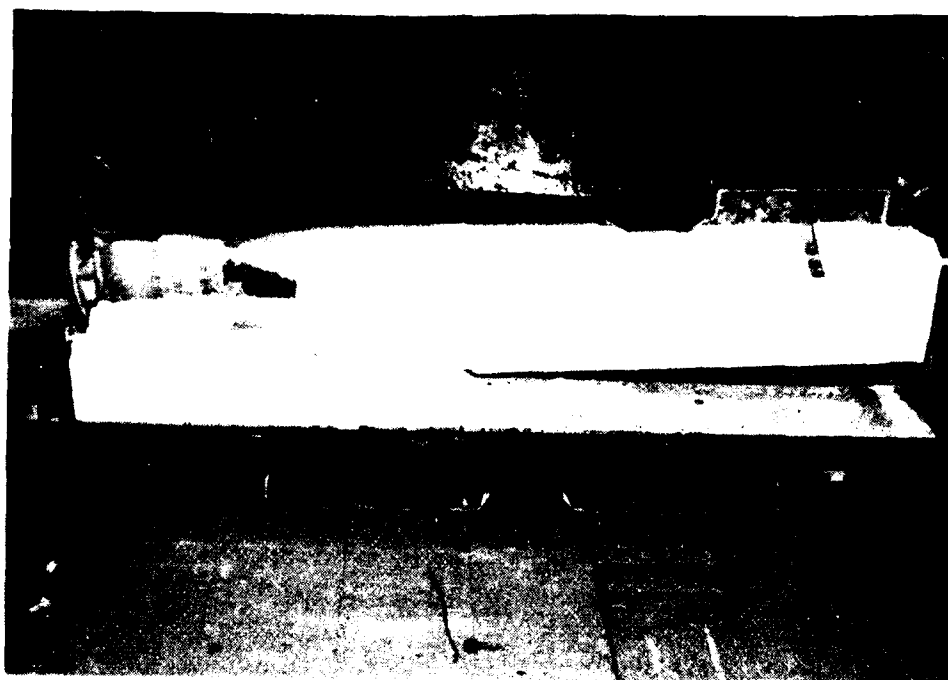


FIGURE 13. CRADLE CUSHION, TORN AND UNGLUED.

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

1a. REPORT SECURITY CLASSIFICATION UNCLASSIFIED			1b. RESTRICTIVE MARKINGS		
2a. SECURITY CLASSIFICATION AUTHORITY NONE			3. DISTRIBUTION/AVAILABILITY OF REPORT Approved for Public Release Distribution Unlimited		
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE					
4. PERFORMING ORGANIZATION REPORT NUMBER(S) DSTZ 88-R-07			5. MONITORING ORGANIZATION REPORT NUMBER(S)		
6a. NAME OF PERFORMING ORGANIZATION		6b. OFFICE SYMBOL (if applicable)	7a. NAME OF MONITORING ORGANIZATION		
6c. ADDRESS (City, State, and ZIP Code) HQ AFLC/DSTZ Wright-Patterson AFB OH 45433-5999			7b. ADDRESS (City, State, and ZIP Code)		
8a. NAME OF FUNDING/SPONSORING ORGANIZATION		8b. OFFICE SYMBOL (if applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER		
8c. ADDRESS (City, State, and ZIP Code)			10. SOURCE OF FUNDING NUMBERS		
PROGRAM ELEMENT NO.		PROJECT NO.	TASK NO.	WORK UNIT ACCESSION NO.	
11. TITLE (Include Security Classification) Evaluation of Engineering Change Proposals 10 and 31 and Performance Oriented Packaging Testing of CNU-399/425 Fiberglass Maverick Missile Container					
12. PERSONAL AUTHOR(S) Susan M. Hughey					
13a. TYPE OF REPORT Final		13b. TIME COVERED FROM Sep 88 TO Dec 88		14. DATE OF REPORT (Year, Month, Day)	
15. PAGE COUNT					
16. SUPPLEMENTARY NOTATION					
17. COSATI CODES			18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)		
FIELD	GROUP	SUB-GROUP	CNU-399/425, Performance Oriented Packaging Testing United Nations' Testing, Fiberglass Maverick Missile		
19. ABSTRACT (Continue on reverse if necessary and identify by block number)					
<p>Aeronautical Systems Division, ASD/SDML, requested assistance from the Air Force Packaging Evaluation Activity to conduct testing on the CNU-399E/425E fiberglass Maverick missile container for engineering change proposals and performance oriented packaging.</p> <p>The CNU-399E/425E container was designed and fabricated by Plastics Research Corporation, 13538 Excelsior Dr., Santa Fe Springs CA 90670. The containers are environmentally sealed with a humidity indicator, desiccant port, and a pressure relief valve. The containers are designed to protect one AGM-65A/B/C/D/E/F all-up-round Maverick missile during world-wide shipment, storage, and handling. The containers will also be</p>					
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT <input type="checkbox"/> UNCLASSIFIED/UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS			21. ABSTRACT SECURITY CLASSIFICATION Unclassified		
22a. NAME OF RESPONSIBLE INDIVIDUAL Susan M. Hughey			22b. TELEPHONE (Include Area Code) (513) 257-3362		22c. OFFICE SYMBOL HQ AFIC/DSTZD

19. (Continued)

used for one missile without the guidance unit and for one missile without the guidance unit and the hydraulic actuation system. The CNU-425/E is the Air Force version of the container. The CNU-399/E is the Navy version and differs from the CNU-425/E only in some external Navy-specific handling features.

The test plan used for these containers was derived from ASD/SDML Specification Number CON 319 dated 30 May 86, Federal Test Method Standard No. 101, U.N. Standard (Ref. ICAD 4.3).

Results of the tests conducted on the containers were acceptable. The container's cradle system did not crack during the rough handling tests and the containers did successfully pass the POP tests, as prescribed by the UN test criteria.

DISTRIBUTION LIST

DTIC/FDAC Cameron Station Alexandria, VA 22304-6145	12
HQ AFLC/DSTZ Library Wright-Patterson AFB OH 45433-5999	20
HQ AFLC/DS Wright-Patterson AFB OH 45433-5999	2
HQ AFLC/DST Wright-Patterson AFB OH 45433-5999	2
HQ AFLC/DSTTP Wright-Patterson AFB OH 45433-5999	2
HQ USAF/LETT Washington DC 20330	1
HQ AFSC/LGT Andrews AFB MD 20334-5000	1
OC-ALC/DST Tinker AFB OK 73145	1
OO-ALC/DST Hill AFB UT 84406	2
SA-ALC/DST Kelly AFB TX 78241	1
SM-ALC/DST McClellan AFB CA 95652	1
WR-ALC/DST Robins AFB GA 31098	1
ASD/AWL Wright-Patterson AFB OH 45433	1
ASD/ALXP Wright-Patterson AFB OH 45433	2
AFSC AD/YBA Eglin AFB FL 32542	2
GSA, Office of Engineering Mgt Packaging Division Washington DC 20406	1

DISTRIBUTION LIST (Cont'd)

Commander Naval Supply Systems Command Attn: N. Karl (SUP 0611F) Washington DC 20376-5000	1
Commander Naval Air Systems Command Attn: E. Panigot (AIR 41212A) Washington DC 20361	1
Commander Space and Naval Warfare Systems Command Attn: T. Corbe (Code 8218) Washington DC 20360	1
Commander Naval Facilities Engineering Command Hoffman Bldg. #2, Room 12S21 Attn: C. Manwarring (FAC 0644) Alexandria, VA 22332	1
Commanding Officer Naval Construction Battalion Center Attn: K. Pollock (Code 15611K) Port Hueneme, CA 93043	1
Commander Naval Sea Systems Command Attn: G. Mustin (SEA 66P) Washington DC 20362	1
Commander Naval Sea Systems Command Attn: F. Basford (SEA 05M3) Washington DC 20362	1
Commanding Officer Naval Aviation Supply Office 700 Robbins Avenue Attn: J. Yannello (Code EPP-A) Philadelphia, PA 19111-5098	1
Commanding Officer Navy Ships Parts Control Center P.O. Box 2020 Attn: F. Sechrist (Code 0541) Mechanicsburg, PA 17055-0788	1

DISTRIBUTION LIST (Cont'd)

Commanding Officer Naval Air Engineering Center Attn: F. Magnifico (SESD Code 9321) Lakehurst, NJ 08733-5100	1
Commanding Officer Naval Weapons Station Earle NWHC/Code 8023 Colts Neck, NJ 07722-5000	2
ASO/TEP-A 4030 700 Robbins Ave Philadelphia, PA 19111	1
US AMC Packaging, Storage, and Containerization Center/SDSTO-T Tobyhanna, PA 18466-5097	1
DLSIE/AMXMC-D US Army Logistics Mgt Ctr Ft Lee VA 23801-6034	1
US Army ARDEC/SMCAR-AEP Attn: Mike Ivankoe Dover, NJ 07801-5001	1
US Army Natick Labs/STRNC-ES Natick MA 01760	1
HQ DLA/OWP Cameron Station Alexandria, VA 22304-6100	1
HQ AFLC/MMA Wright-Patterson AFB OH 45433	2
AFALC/CV Wright-Patterson AFB OH 45433	2
AFALC/OA Wright-Patterson AFB OH 45433	2
AFLC LOC/CV Wright-Patterson AFB OH 45433	2
AFLC LOC/TL Wright-Patterson AFB OH 45433	2
ASD/SDM Wright-Patterson AFB OH 45433	2

DISTRIBUTION LIST (Cont'd)

HQ TAC/LGWL	2
Langley AFB, VA 23665	
OO-ALC/DSTD	2
Hill AFB, UT 84056	
OO-ALC/MMWMM	2
Hill AFB, UT 84056-5609	